

Received:08/22/2014 Completed:08/27/2014 Letter: C AM P.O.#: Test Report #: 3-03859-0-

Client's Identification Style: Showstopper Event Tent Canopy. Content: 400 Denier Polyester. Width: 120". End Use: Outdoors.

Tested For: **Jeff Spinner** Key Test: NFPA 701-2010 TM#2 Flat 425  
Sign-Zone, Inc.  
6400 Bunker Lake Blvd NW Tel: 1-(763)-746-1115 Ext:  
Ramsey, MN 55303 Fax: 1-(763)-746-1133

PC:1H

TEST PERFORMED: NFPA 701 - Standard Methods of Fire Tests for Flame Propagation of Textiles and Films - 2010 Edition - Test Method #2 - Flat Sheet Specimens

SPECIMEN CONFIGURATION:  Single Layer;  Multi Layer

RESULTS REPORTED:  Initially  After 72 hours water leaching  
 After 3 dry cleanings  After 100 hours accelerated weathering  
 After 5 launderings @ 160°F

RESULTS:

Length Specimen #	Afterflame (seconds)	Drip Burn (seconds)	Char Length (mm)
1	0	0	138
2	0	0	134
3	0	0	143
4	0	0	133
5	0	0	158
6	0	0	153
7	0	0	154
8	0	0	148
9	0	0	140
10	0	0	128

APPROXIMATE WEIGHT OF MATERIAL (as measured by Govmark): 223 g/m<sup>2</sup>

FAILURE CRITERIA: For each individual specimen --

Afterflame	Drip Burn	Char Length
Exceeds 2.0 seconds	Exceeds 2.0 seconds	Exceeds 435 mm (17.1")

RETEST PROVISION: Test 5 additional specimens if only 1 specimen fails.

CONCLUSION: Based on the above Results and Failure Criteria, the item tested:

Passes;  Fails;  Requires testing of 5 additional specimens

Received: 08/22/2014	Completed: 08/27/2014	Letter: C	AM	P.O.#:	Test Report #:	3-03859-0-
Client's Identification	Style: Showstopper Event Tent Canopy. Content: 400 Denier Polyester. Width: 120". End Use: Outdoors.					
Tested For: <b>Jeff Spinner</b>	Sign-Zone, Inc. 6400 Bunker Lake Blvd NW Ramsey, MN 55303				Key Test: NFPA 701-2010 TM#2 Flat	425
				Tel: 1-(763)-746-1115	Ext:	
				Fax: 1-(763)-746-1133		


PRECONDITIONING:     1 hr @ 220°F (Standard)  
                                24 hrs @ 68±9°F (Alternate: Material shrinks/distorts @ 220°F)

REMARKS: None.

CONVERSION FACTORS:

mm ÷ 25.4 = inches  
 g/m<sup>2</sup> ÷ 28.35 x .835 = oz/yd<sup>2</sup>

CERTIFICATION: I certify that the above results were obtained after testing specimens in accordance with the procedures and equipment specified by NFPA 701 - 2010 Edition Test Method #2 Flat Sheet Specimens.

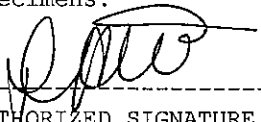

AUG 29 2014

-----  
 AUTHORIZED SIGNATURE  
 THE GOVMARK ORGANIZATION, INC. /pm

106

**MS. PHYLLIS PETTIT**

(Page 2 of 2)